
THE AVIATION POINT · THEAVIATIONPOINT.COM · THE AVIATION POINT · THEAVIATIONPOINT.COM

The Aviation Point.

CP Titanium Grade 1

The softest and most formable titanium: 35 ksi minimum tensile.

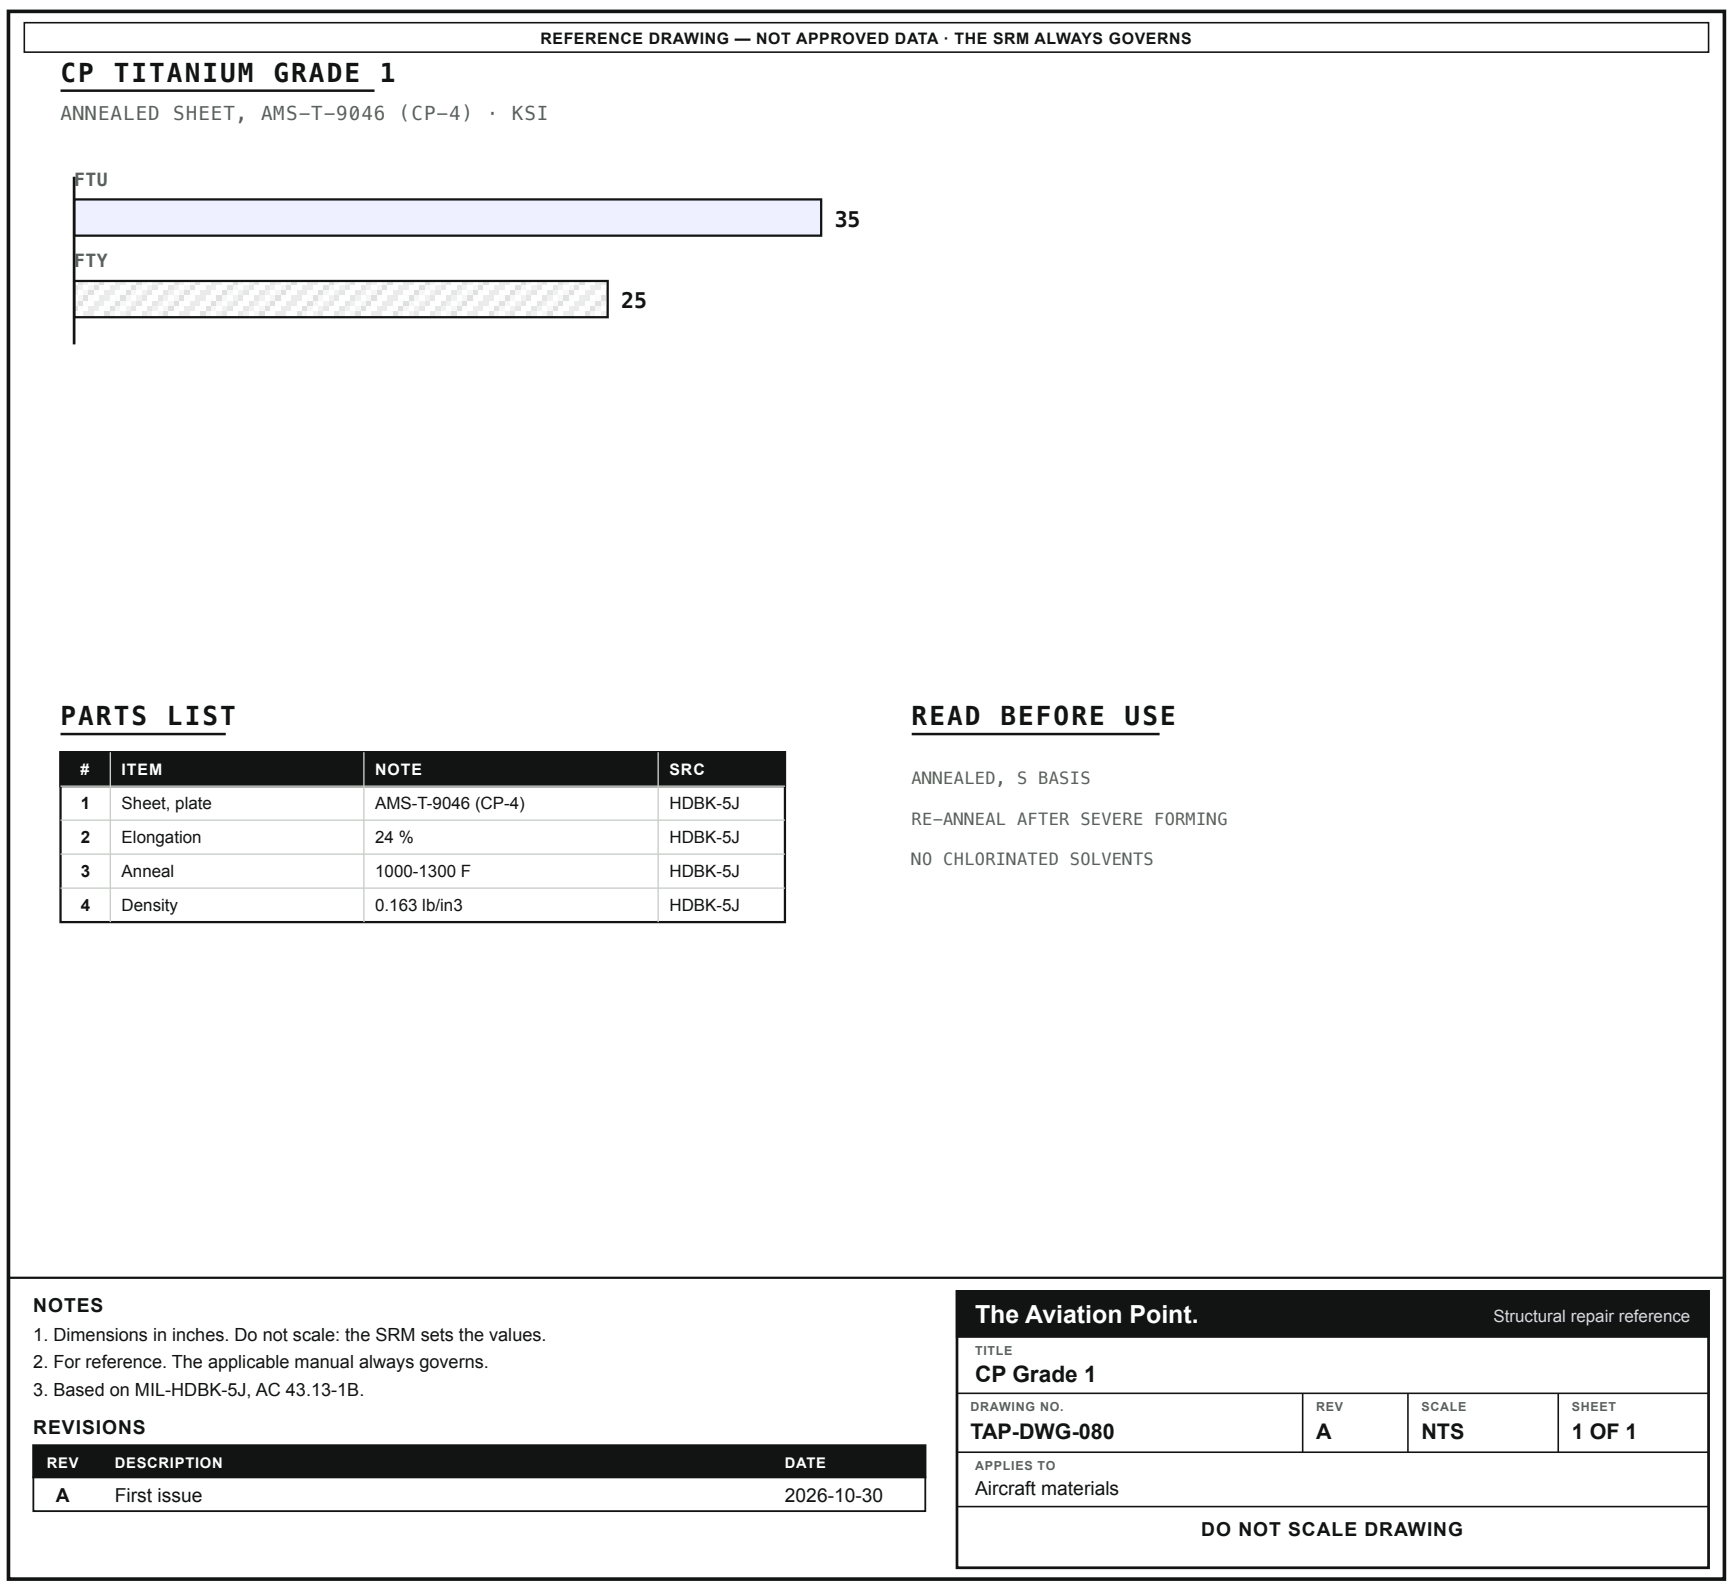

CP titanium Grade 1: annealed sheet, AMS-T-9046 (CP-4) Values from MIL-HDBK-5J, S basis unless noted.

Key facts

Property	Value	Source
Type	Unalloyed titanium, annealed; excellent formability, readily welded or brazed	MIL-HDBK-5J, par. 5.2.1.0
MIL-HDBK-5J name	CP-4 under AMS-T-9046, equal in strength to ASTM Grade 1	MIL-HDBK-5J, Table 5.2.1.0(b); ASTM B265 grade strengths
Specification	AMS-T-9046 (CP-4)	MIL-HDBK-5J, Table 5.2.1.0(a)
Oxygen limit	0.18 % max (interstitials set the grade)	ASTM B265-10 Table 2 (Grade 1)
Full anneal	1,000 to 1,300 °F for 10 to 30 minutes	MIL-HDBK-5J, par. 5.2.1.0
Stress relief	900 to 1,000 °F for 30 minutes	MIL-HDBK-5J, par. 5.2.1.0
Density	0.163 lb/in³ (about 4.51 g/cm³, converted)	MIL-HDBK-5J, Table 5.2.1.0(b)

Design allowables — CP titanium Grade 1 sheet, strip and plate, annealed

Property	S basis	Unit
Ftu, L and LT	35	ksi
Fty, L and LT	25	ksi
Elongation, L and LT (0.025 in and over)	24	%
E	15.5	10³ ksi
G	6.5	10³ ksi
Density	0.163	lb/in³

Key points

- **Annealed values.** Forming and heat change them.
- **Not a substitute for an alloy grade** or for aluminum; the drawing names the grade.

SOURCES · FAA AC 43.13-1B CHG 1 · FAA-H-8083-31B, Aviation Maintenance Technician Handbook, Airframe, Volume 1 · MIL-HDBK-5J, Metallic Materials and Elements for Aerospace Vehicle Structures · FAA AC 43.13-1B CHG 1 · MMPDS · ASTM B265, Titanium and Titanium Alloy Strip, Sheet, and Plate

SCAN · OPEN THIS GUIDE
theaviationpoint.com/materials/titanium/cp-grade-1/

Educational reference only, not approved data. Always consult the applicable SRM, AMM, or AC 43.13-1B and your certifying authority.